

Crack Roughness in the 2D Random Threshold Beam Model

Phani K.V.V. Nukala

Computer Science and Mathematics Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831-6164, USA

Stefano Zapperi

*CNR-INFM, S3, Dipartimento di Fisica, Università di Modena e Reggio Emilia, Via G. Campi 213A, 41100 Modena, Italy and
ISI Foundation, Viale S. Severo 65, 10133 Torino, Italy*

Mikko J. Alava

Department of Engineering of Physics, Helsinki University of Technology, FIN-02015 HUT, Finland

Srđan Šimunović

Computer Science and Mathematics Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831-6164, USA

We study the scaling of two-dimensional crack roughness using large scale beam lattice systems. Our results indicate that the crack roughness obtained using beam lattice systems does not exhibit anomalous scaling in sharp contrast to the simulation results obtained using scalar fuse lattices. The local and global roughness exponents (ζ_{loc} and ζ , respectively) are equal to each other, and the two-dimensional crack roughness exponent is estimated to be $\zeta_{loc} = \zeta = 0.64 \pm 0.02$. Removal of overhangs (jumps) in the crack profiles eliminates even the minute differences between the local and global roughness exponents. Furthermore, removing these jumps in the crack profile completely eliminates the multiscaling observed in other studies. We find that the probability density distribution $p(\Delta h(\ell))$ of the height differences $\Delta h(\ell) = [h(x + \ell) - h(x)]$ of the crack profile obtained after removing the jumps in the profiles follows a Gaussian distribution even for small window sizes (ℓ).

I. INTRODUCTION

Understanding the scaling properties of fracture surfaces still represents an unsolved problem despite two decades of intense research activities [1, 2]. Experiments on several materials under different loading conditions have shown that the fracture surface is self-affine [3] and can be characterized by a roughness exponent ζ . Experiments on several materials including metals [4], glass [5], rocks [6] and ceramics [7], have shown a universal out of plane roughness exponent of $\zeta \simeq 0.8$ for three-dimensional fracture surfaces irrespective of the material studied, as reviewed in Ref. [8]. Recent experimental evidence shows, however, that the picture is more complicated: such scaling is valid at small and intermediate scales in the so-called fracture process zone (FPZ), while at large scales one observes a new regime with $\zeta \simeq 0.4$ attributed to crack line depinning [9, 10, 11]. Recent numerical investigations of the random fuse model indicate that the local roughness exponent in two dimensions does not depend on the size of the FPZ, but only on the fact that a FPZ is present or not [12].

In addition, it is by no means a priori clear that "simple" self-affinity is sufficient to describe the experiments. It has been argued that fracture surfaces may exhibit anomalous scaling [13]: the *global* exponent describing the scaling of the crack width with the sample size is larger than the local exponent measured on a single sample [14, 15]. In this sense, it is necessary to introduce two roughness exponents a global exponent (ζ) and a local exponent (ζ_{loc}) to define the roughness of fracture surfaces. Anomalous scaling is noted in the numerical

simulations as well [16, 17]; however, its origin is not clear yet although in experiments it is conjectured to be an artifact of initial transient regime as the fracture front moves away from the initial notch [11]. Recent studies [18, 19] also suggest that the origin of anomalous scaling in numerical simulations in two dimensions may also be due to the existence of overhangs (jumps) in the crack profile, originating from crack branching. As a further complication, there is an on-going debate whether fracture surfaces exhibit multi-affine scaling [18, 19, 20, 21], implying that one would observe a whole family of roughness exponents ζ_q depending on which statistical moment q of the correlation function is measured.

The theoretical understanding of the origin and universality of crack surface roughness is often investigated by discrete lattice (fuse, central-force, and beam) models [2]. In these models the elastic medium is described by a network of discrete elements such as fuses, springs and beams with random failure thresholds. In the simplest approximation of a scalar displacement, one recovers the random fuse model (RFM) where a lattice of fuses with random threshold are subject to an increasing external voltage [22]. Using two-dimensional RFM, the estimated crack surface roughness exponents are: $\zeta = 0.7 \pm 0.07$ [23], $\zeta_{loc} = 2/3$ [24], and $\zeta = 0.74 \pm 0.02$ [25]. Recently, using large system sizes (up to $L = 1024$) with extensive sample averaging, we found that the crack roughness exhibits anomalous scaling [26]. In particular, the local and global roughness exponents estimated using two different lattice topologies are: $\zeta_{loc} = 0.72 \pm 0.02$ and $\zeta = 0.84 \pm 0.03$. The reasons behind the origin of anomalous scaling in numerical simulations are not yet clear, although the existence of overhangs in the crack pro-

file is expected to have contributed to anomalous scaling [18, 19]. In comparison, the roughness exponents obtained from quasi two-dimensional experiments, mainly obtained for paper samples, indicate a roughness exponent in the range $\zeta \simeq 0.6 - 0.7$ [18, 20, 27, 28, 29, 30], but occasionally significantly higher values have also been reported [31]. It is not known at this time whether this variation in ζ values is a reflection of practical difficulties in experimentally measuring ζ - in paper it is difficult to have a scaling range spanning over several decades since the structure becomes three-dimensional at small scales (0.1 mm) and at the millimeter range the fiber length interferes - or that the roughness exponent is not really universal but depends on material parameters and the anisotropy of the medium.

Despite this reasonable agreement between the numerical results obtained using two-dimensional RFM and the above quasi-two-dimensional experimental results, a lingering question is whether scalar representation of the elastic medium using random fuse models is an adequate representation of fracture. Moreover, it is an intriguing question whether the same roughness exponents as those obtained using RFM will be obtained using more complex random threshold central-force (spring) and beam models. Using central-force models, a roughness exponent of 0.65 ± 0.07 is obtained in Ref. [32]. A more recent study with a range of disorder strengths in random thresholds estimated the local and global roughness exponents to be in the range $0.5 - 0.67$ and $0.6 - 0.85$, respectively [19]. Using two-dimensional beam simulations, Ref. [33] estimated a typical value for the global roughness exponent to be 0.86; however, the roughness exponent is argued to be disorder dependent. Similar disorder dependent roughness exponents have also been reported recently for the RFM [34]. These results were obtained in the square lattice and were attributed to a lattice effect at low disorder. They indeed disappear for triangular lattice, where the roughness exponent is the same independent on disorder [12].

The questions we address in this article are the following: (i) whether anomalous scaling is present in two-dimensional fracture simulations using beam lattice systems, and (ii) whether roughness exponents so measured using beam lattice systems are in agreement with those obtained using simplified scalar RFM models. Along the way, we also address why scalar RFM models have been successful in representing fracture in a disordered elastic medium. Recent studies [18, 20, 29] have shown that multi-affinity of fracture surfaces is an artifact of overhangs (or jumps) in the crack profile. Here, we further investigate the influence of these overhangs in the crack profiles on crack roughness exponents. This article has three further Sections: in the next one, we describe the beam model used. In Section III, we present the numerical results obtained with it. Finally, Section IV concludes the paper.

II. BEAM MODEL

The random thresholds beam model (RBM) we consider in this study is a two-dimensional triangle lattice system of size $L \times L$. Unlike the scalar RFM model, the vectorial RBM has three degrees of freedom (x-translation u , y-translation v , and a rotation θ about z axis) at each of the lattice nodes (sites), and each of the bonds (beams) in the lattice connects two nearest neighbour nodes. We assume that the beams are connected rigidly at each of the nodes such that the angle between any two beams connected at a node remains unaltered during the deformation process. These nodal displacements and rotations introduce conjugate forces and bending moments in the beam members. Using Timoshenko beam theory [35], which includes shear deformations of the beam cross-section in addition to the usual axial deformation of cross-sections, the *local* stiffness matrix for a beam element that relates the local nodal displacements and rotations to local nodal forces and bending moments in the beam's *local* coordinate system is given by

$$\mathbf{K}_{local} = \begin{bmatrix} \frac{EA}{\ell_b} & 0 & 0 & -\frac{EA}{\ell_b} & 0 & 0 \\ 0 & \frac{12EI}{(1+\alpha)\ell_b^3} & \frac{6EI}{(1+\alpha)\ell_b^2} & 0 & -\frac{12EI}{(1+\alpha)\ell_b^3} & \frac{6EI}{(1+\alpha)\ell_b^2} \\ 0 & \frac{6EI}{(1+\alpha)\ell_b^2} & \frac{(4+\alpha)EI}{(1+\alpha)\ell_b} & 0 & -\frac{6EI}{(1+\alpha)\ell_b^2} & \frac{(2-\alpha)EI}{(1+\alpha)\ell_b} \\ SYM & & & \frac{EA}{\ell_b} & 0 & 0 \\ 0 & -\frac{12EI}{(1+\alpha)\ell_b^3} & -\frac{6EI}{(1+\alpha)\ell_b^2} & 0 & \frac{12EI}{(1+\alpha)\ell_b^3} & -\frac{6EI}{(1+\alpha)\ell_b^2} \\ 0 & \frac{6EI}{(1+\alpha)\ell_b^2} & \frac{(4+\alpha)EI}{(1+\alpha)\ell_b} & 0 & -\frac{6EI}{(1+\alpha)\ell_b^2} & \frac{(2-\alpha)EI}{(1+\alpha)\ell_b} \end{bmatrix} \quad (1)$$

where E is the Young's modulus, G is the shear modulus, A is the beam cross-sectional area, I is the moment of inertia of beam cross-section, ℓ_b is the length of the beam, and $\alpha = \frac{12EI}{GA\ell_b^2}$ is the shear correction factor, which denotes the ratio of bending stiffness to the shear stiffness. If shear deformation of beam cross-section is negligible, then $\alpha = 0$ and the Timoshenko's beam theory reduces to Euler-Bernoulli beam theory. Equation 1 presents a relation between local nodal displacements and rotations $\mathbf{d}_\ell = (u_{li}, v_{li}, \theta_{li}, u_{lj}, v_{lj}, \theta_{lj})^T$ and local forces and moments $\mathbf{F}_\ell = (F_{li}, V_{li}, M_{li}, F_{lj}, V_{lj}, M_{lj})^T$. In this setting, the subscript l refers to local quantities, the superscript T represents transpose of a vector or a matrix, i and j refer to i -th and j -th nodes of the beam, and F , V , and M refer to axial force, shear force, and bending moments respectively.

Computing the equilibrium of the lattice system is achieved by first transforming these local quantities ($\mathbf{d}_\ell$ and $\mathbf{F}_\ell$) into global quantities $\mathbf{d} = (u_i, v_i, \theta_i, u_j, v_j, \theta_j)^T$ and $\mathbf{F} = (F_i, V_i, M_i, F_j, V_j, M_j)^T$ through a coordinate transformation $\mathbf{T}$ such that $\mathbf{d}_\ell = \mathbf{T}\mathbf{d}$, $\mathbf{F}_\ell = \mathbf{T}\mathbf{F}$, and $\mathbf{K} = \mathbf{T}^T \mathbf{K}_{local} \mathbf{T}$, and then satisfying equilibrium equations at each node such that

$$\Sigma_{\langle ij \rangle} F_x = 0; \quad \Sigma_{\langle ij \rangle} F_y = 0; \quad \Sigma_{\langle ij \rangle} M = 0 \quad (2)$$

where $\Sigma_{\langle ij \rangle}$ implies that the summation is carried over all the intact bonds $\langle ij \rangle$ joining at node i . In the

above discussion, the transformation matrix $\mathbf{T}$ is given by

$$\mathbf{T} = \begin{bmatrix} \mathbf{Q} & \mathbf{0} \\ \mathbf{0} & \mathbf{Q} \end{bmatrix} \quad (3)$$

where

$$\mathbf{Q} = \begin{bmatrix} c & s & 0 \\ -s & c & 0 \\ 0 & 0 & 1 \end{bmatrix} \quad (4)$$

and $c = \cos(\beta)$, $s = \sin(\beta)$ refer to the direction cosines of the beam with β representing the angle between the beam axis and the x -direction.

In this RBM, we start with a fully intact lattice system with beams having unit length, unit square cross-section and Young's modulus $E = 1$. This results in a unit axial stiffness ($EA/\ell_b = 1$) and bending stiffness ($12EI/\ell_b^3 = 1$) for each of the beams in the lattice system. Since the beam can deform in two independent deformation modes (axial and bending), we assume randomly distributed bond breaking axial and bending thresholds, t_a and t_b , based on thresholds probability distributions, $p_a(t_a)$ and $p_b(t_b)$ respectively. The failure criterion for a beam is defined through an axial force and bending moment interaction equation (similar to von-Mises criterion in metal plasticity) given by

$$r \equiv \left(\frac{F}{t_a}\right)^2 + \frac{\max(|M_i|, |M_j|)}{t_b} = 1 \quad (5)$$

The beam breaks irreversibly, whenever the failure criterion $r \geq 1$. Periodic boundary conditions are imposed in the horizontal direction and a constant unit displacement difference is applied between the top and the bottom of lattice system.

Numerically, a unit displacement, $\Delta = 1$, is applied at the top of the lattice system and the equilibrium equations (Eq. 2) are solved to determine the force in each of the springs. Solution of Eq. 2 results in global displacements and rotations $\mathbf{d}$, using which the local displacements $\mathbf{d}_\ell = \mathbf{T}\mathbf{d}$ and the local forces $\mathbf{F}_\ell = \mathbf{K}_{local}\mathbf{d}_\ell$ are computed for each of the intact beams. Subsequently, for each bond k with nodes i and j , the quantities $a_k = \left(\frac{F}{t_a}\right)^2$ and $b_k = \frac{\max(|M_i|, |M_j|)}{t_b}$ are evaluated, and the bond k_c having the smallest value,

$$r_k = \frac{-b_k + \sqrt{b_k^2 + 4a_k}}{2a_k} \quad (6)$$

is irreversibly removed (When $a_k = 0$, then $r_k = \frac{1}{b_k}$). The forces are redistributed instantaneously after a bond is broken implying that the stress relaxation in the lattice system is much faster than the breaking of a bond. Each time a bond is broken, it is necessary to re-equilibrate the lattice system in order to determine the subsequent breaking of a bond. The process of breaking of a bond, one at a time, is repeated until the lattice system falls

apart. For the RBM, we consider a uniform probability distribution in $[0, 1]$ for both axial and bending thresholds disorders.

Numerical simulations of fracture using lattice networks have often been limited to smaller system sizes due to the high computational cost associated with solving a new large set of linear equations every time a new lattice bond is broken. In this work, we use the multiple-rank sparse Cholesky factorization downdating algorithm developed by the authors for simulating fracture using discrete beam lattice systems [36, 37]. For two-dimensional systems, this low-rank Cholesky factor downdating algorithm is significantly faster than competing preconditioned conjugate-gradient based iterative solvers. Using this numerical algorithm, we were able to investigate fracture in larger lattice systems (e.g., $L = 320$ in 2D) than those investigated in previous studies. The lattice system sizes considered in this work are $L = \{32, 64, 128, 256, 320\}$ with large numbers of sample configurations, $N_{config} = \{2000, 4000, 640, 400, 200\}$ respectively, in order to reduce the statistical error in the numerical results.

III. CRACK ROUGHNESS

Once the sample has failed, we identify the final crack, which typically displays dangling ends (see Fig. 1). We remove them and obtain a single valued crack line h_x , where the values of $x \in [0, L]$. For self-affine cracks, the local width, $w(l) \equiv \langle \sum_x (h_x - (1/l) \sum_X h_X)^2 \rangle^{1/2}$, where the sums are restricted to regions of length l and the average is over different realizations, scales as $w(l) \sim l^\zeta$ for $l \ll L$ and saturates to a value $W = w(L) \sim L^\zeta$ corresponding to the global width. The power spectrum $S(k) \equiv \langle \hat{h}_k \hat{h}_{-k} \rangle / L$, where $\hat{h}_k \equiv \sum_x h_x \exp i(2\pi x k / L)$, decays as $S(k) \sim k^{-(2\zeta+1)}$. When anomalous scaling is present [13, 14, 15], the exponent describing the system size dependence of the surface differs from the local exponent measured for a fixed system size L . In particular, the local width scales as $w(\ell) \sim \ell^{\zeta_{loc}} L^{\zeta - \zeta_{loc}}$, so that the global roughness W scales as L^ζ with $\zeta > \zeta_{loc}$. Consequently, the power spectrum scales as $S(k) \sim k^{-(2\zeta_{loc}+1)} L^{2(\zeta - \zeta_{loc})}$.

Recently, Bouchbinder et al. [21] have suggested that the crack line $h(x)$ is not self-affine; instead, it exhibits a much complicated multi-affine (or multiscaling) structure. This implies a non-constant scaling exponent ζ_q for the q -th order correlation function $C_q(\ell) = \langle |h(x+\ell) - h(x)|^q \rangle^{1/q} \sim \ell^{\zeta_q}$ [21]. This would imply the breakdown of self-affinity. Recent studies [18, 20, 29] have shown that multi-affinity of fracture surfaces seems to disappear on large enough scales ℓ , however.

As shown in Fig. 2, removal of jumps from an initially periodic crack profile $h(x)$ makes the resulting crack profile $h_{NP}(x)$ nonperiodic, where the subscript NP refers to *nonperiodicity* of the profiles. A direct evaluation of the roughness exponent using these nonperiodic profiles

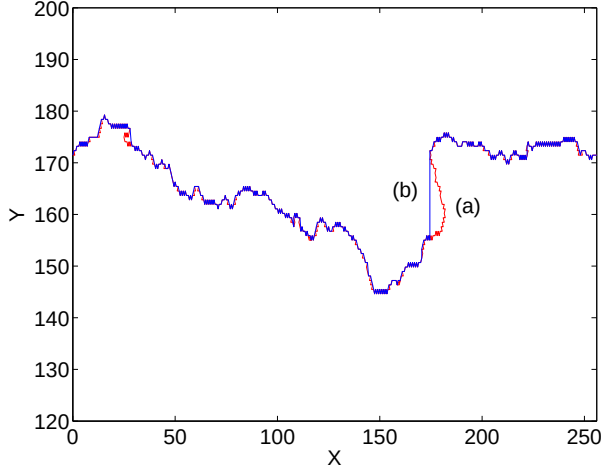


FIG. 1: (Color online) A typical crack in a system of size $L \times L$ with $L = 256$. This crack, identified as (a) in the figure, has dangling ends, which are removed to obtain a single valued crack profile $h(x)$, identified as (b) in the figure. However, this final crack $h(x)$ possesses finite jumps that arise due to solid-on-solid projection of fracture surfaces.

can be made. However, such an evaluation of roughness exhibits finite size effects for window sizes $\ell > L/2$ due to nonperiodicity. Alternatively, the roughness of these resulting profiles can be evaluated by first subtracting a linear profile $h_{lin}(x) = [h_{NP}(0) + \frac{(h_{NP}(L) - h_{NP}(0))}{L}x]$ from the nonperiodic profile $h_{NP}(x)$, and then evaluating the roughness of the resulting periodic profile $h_P(x)$.

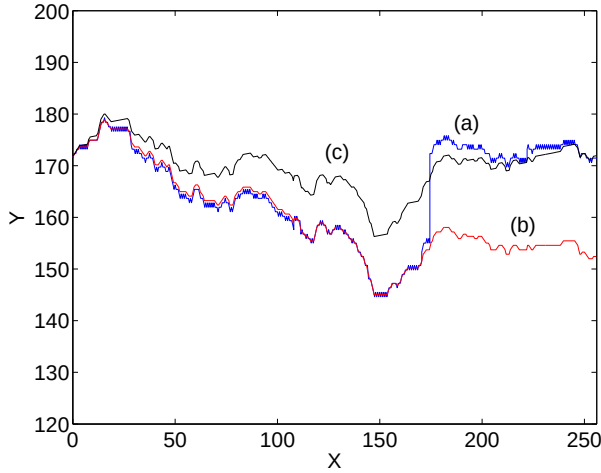


FIG. 2: (Color online) Figure shows a typical single valued crack profile $h(x)$ with jumps based on solid-on-solid projection scheme (identified as (a)). Removing the jumps in the crack profile $h(x)$ makes it a non-periodic profile (identified as (b)). Subtracting a linear profile from this non-periodic profile results in a periodic profile (identified as (c)).

Figure 3a presents the scaling of crack width $w(\ell)$ with window size ℓ . The inset and the main figure respectively

show the crack widths calculated based on original crack profiles with jumps and those obtained from crack profiles without the jumps. The jumps in the profiles appear to result in slightly different local and global roughness exponents (ζ_{loc} and ζ , respectively), although the exponents are within error bars. However, removing these jumps in the crack profiles leads to a single roughness exponent of $\zeta_{loc} = \zeta = 0.65$ suggesting that anomalous scaling is an artifact of jumps in the crack profiles, at least for fracture simulations based on beam lattice systems. We have also investigated the power spectra $S(k)$ of the crack profiles with and without the jumps in the crack profiles (see Fig. 3b). Collapse of the power spectra for different system sizes can be observed for both the sets of crack profiles and the roughness exponents ($\zeta_{loc} = \zeta = 0.65$) obtained using the power law fits to the data are consistent with those presented in Fig. 3a.

The self-affine property of the crack profiles also implies that the probability density distribution $p(\Delta h(\ell))$ of the height differences $\Delta h(\ell) = [h(x + \ell) - h(x)]$ of the crack profile follows the relation

$$p(\Delta h(\ell)) \sim \langle \Delta h^2(\ell) \rangle^{-1/2} f\left(\frac{\Delta h(\ell)}{\langle \Delta h^2(\ell) \rangle^{1/2}}\right) \quad (7)$$

Noting that periodicity in crack profiles is analogous to return-to-origin excursions arising in stochastic processes, we propose the following ansatz for the local width $\langle \Delta h^2(\ell) \rangle^{1/2}$ in height differences $\Delta h(\ell)$

$$\langle \Delta h^2(\ell) \rangle^{1/2} = \langle \Delta h^2(L/2) \rangle^{1/2} \phi\left(\frac{\ell}{L/2}\right) \quad (8)$$

with $\langle \Delta h^2(L/2) \rangle^{1/2} = L^\zeta$. For periodic profiles, the function $\phi\left(\frac{\ell}{L/2}\right)$ is symmetric about $\ell = L/2$ and is constrained such that $\phi\left(\frac{\ell}{L/2}\right) = 0$ at $\ell = 0$ and $\ell = L$, and $\phi\left(\frac{\ell}{L/2}\right) = 1$ at $\ell = L/2$. Based on these conditions, a scaling ansatz of the form

$$\left[\frac{\langle \Delta h^2(\ell) \rangle^{1/2}}{\langle \Delta h^2(L/2) \rangle^{1/2}}\right]^{1/\zeta_{loc}} + \frac{(\ell - L/2)^2}{(L/2)^2} = 1 \quad (9)$$

similar to stochastic excursions or bridges can be proposed for $\langle \Delta h^2(\ell) \rangle^{1/2}$, which implies a functional form

$$\phi\left(\frac{\ell}{L/2}\right) = \left[1 - \left(\frac{(\ell - L/2)}{L/2}\right)^2\right]^{\zeta_{loc}} \quad (10)$$

for $\phi\left(\frac{\ell}{L/2}\right)$ that is satisfied to a good approximation by our numerical results. This scaling ansatz results in anomalous scaling when $\zeta_{loc} \neq \zeta$. Upon further simplification, Eq. 10 results in

$$\phi\left(\frac{\ell}{L/2}\right) = 4^{\zeta_{loc}} \left(\frac{\ell}{L}\right)^{\zeta_{loc}} \left(1 - \frac{\ell}{L}\right)^{\zeta_{loc}} \quad (11)$$

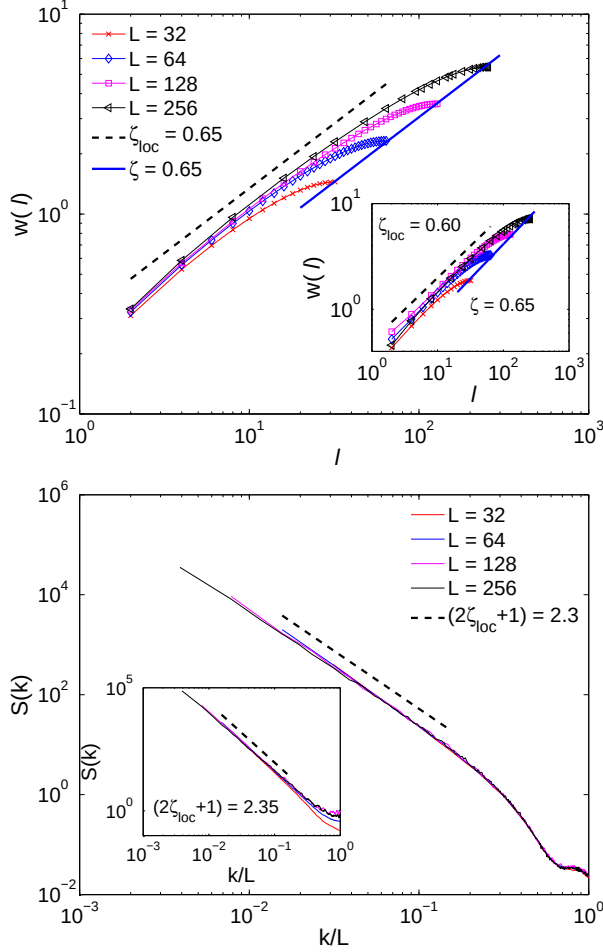


FIG. 3: (Color online) (a) Scaling of crack width $w(\ell)$ with window size ℓ . The inset shows crack widths calculated based on original crack profiles with jumps. The local and global roughness exponents (ζ_{loc} and ζ , respectively) appear to be within error bars although the curves do not collapse. In the main figure, crack widths are calculated based on crack profiles obtained after removing the jumps in the profiles. Removing the jumps in the profiles appears to eliminate the discrepancy between local and global roughness exponents. (b) Scaling of power spectrum $S(k)$. Inset shows the scaling of $S(k)$ for original crack profiles whereas the main figure shows the scaling of $S(k)$ for crack profiles without jumps. Collapse of the power spectrum can be observed, and the exponents are consistent with those shown in (a).

which along with $\langle \Delta h^2(L/2) \rangle^{1/2} = L^\zeta$ and Eq. 8 shows how anomalous scaling arises and how local and global roughness exponents ζ_{loc} and ζ can be computed based on numerical results.

Figure 4 presents the scaling of $\langle \Delta h^2(\ell) \rangle^{1/2}$ based on the above ansatz (Eqs. 8 and 10). The collapse of the $\langle \Delta h_P^2(\ell) \rangle^{1/2} / \langle \Delta h_P^2(L/2) \rangle^{1/2}$ data for different system sizes L and window sizes ℓ onto a scaling form given by Eq. 10 with $\zeta_{loc} = 0.64$ can be clearly seen in Fig. 4(a). In addition, the collapse of the data presented in Fig. 4(c) for $\langle \Delta h_P^q(\ell) \rangle^{1/q} / \langle \Delta h_P^q(L/2) \rangle^{1/q}$ provides quite

concrete evidence that multi-affine scaling of fracture surfaces, similar to what is observed in Ref. [21], is an artifact of jumps in the crack profile that are formed due to the solid-on-solid approximation used in extracting the crack profiles. The results in Fig. 4(c) clearly demonstrate that the removal of these jumps in the crack profiles completely eliminates this apparent multiscaling of fracture surfaces. This is also evident through the scaling of $\langle \Delta h_P^q(L/2) \rangle^{1/q}$ presented in Fig. 4(b). The slopes of the data for moments $q = 1$ to 6 of $\Delta h_P(L/2)$ are identical. It should also be noted that $\langle \Delta h_P^q(L/2) \rangle^{1/q} \sim L^\zeta$ with $\zeta = 0.64$ and is identical to the local roughness exponent as obtained from Figs. 4(a) and (c). This further indicates that anomalous scaling of crack profiles is not present in fracture simulations obtained using the beam lattice systems. As already noted in Figs. 3a-b, the difference between the local and global roughness exponents obtained using the original crack profiles is so small that it already negates the existence of anomalous scaling of crack roughness using beam lattice simulations. Removing the jumps caused by overhangs in the crack profile further reduces even this minute difference in local and global roughness exponents thereby eliminating anomalous scaling of crack profiles.

In the following, we investigate the probability density $p(\Delta h(\ell))$ of height differences $\Delta h(\ell)$. In Refs. [18, 20, 29], the $p(\Delta h(\ell))$ distribution is shown to follow a Gaussian distribution above a cutoff length scale and the deviations away from Gaussian distribution in the tails of the distribution have been attributed to finite jumps in the crack profiles. A self-affine scaling of $p(\Delta h(\ell))$ as given by Eq. 7 implies that the cumulative distribution $P(\Delta h(\ell))$ scales as $P(\Delta h(\ell)) \sim P(\Delta h(\ell) / \langle \Delta h^2(\ell) \rangle^{1/2})$. Figure 5(a) presents the raw data of cumulative probability distributions $P(\Delta h(\ell))$ of the height differences $\Delta h(\ell)$ on a normal or Gaussian paper for bin sizes $\ell \ll L$. As observed in Refs. [18, 20, 29], Fig. 5(a) shows large deviations away from Gaussian distribution for these small bin sizes. However, for moderate ℓ , the distribution is Gaussian with deviations in the tails of the distribution beyond the $3\sigma = 3\langle \Delta h^2(\ell) \rangle^{1/2}$ limit (data not shown in Figure). Removing the jumps in the crack profiles however collapses the $P(\Delta h_P(\ell))$ distributions onto a straight line (see Fig. 5(b)) indicating the adequacy of Gaussian distribution even for small ℓ . Indeed, Fig. 5(b) shows the collapse of the $P(\Delta h_P(\ell))$ data for systems of sizes $L = 128$ and $L = 256$ with a variety of bin sizes $2 \leq \ell \leq L/2$. Removing the jumps in the profiles not only turns the $P(\Delta h_P(\ell))$ distributions Gaussian even for small window sizes ℓ but also extends the validity of $P(\Delta h_P(\ell))$ Gaussian distribution for moderate bin sizes to a $4\sigma = 4\langle \Delta h_P^2(\ell) \rangle^{1/2}$ (99.993% confidence) limit.

IV. DISCUSSION

In summary, the analysis and results presented in this paper indicate that crack profiles obtained in fracture

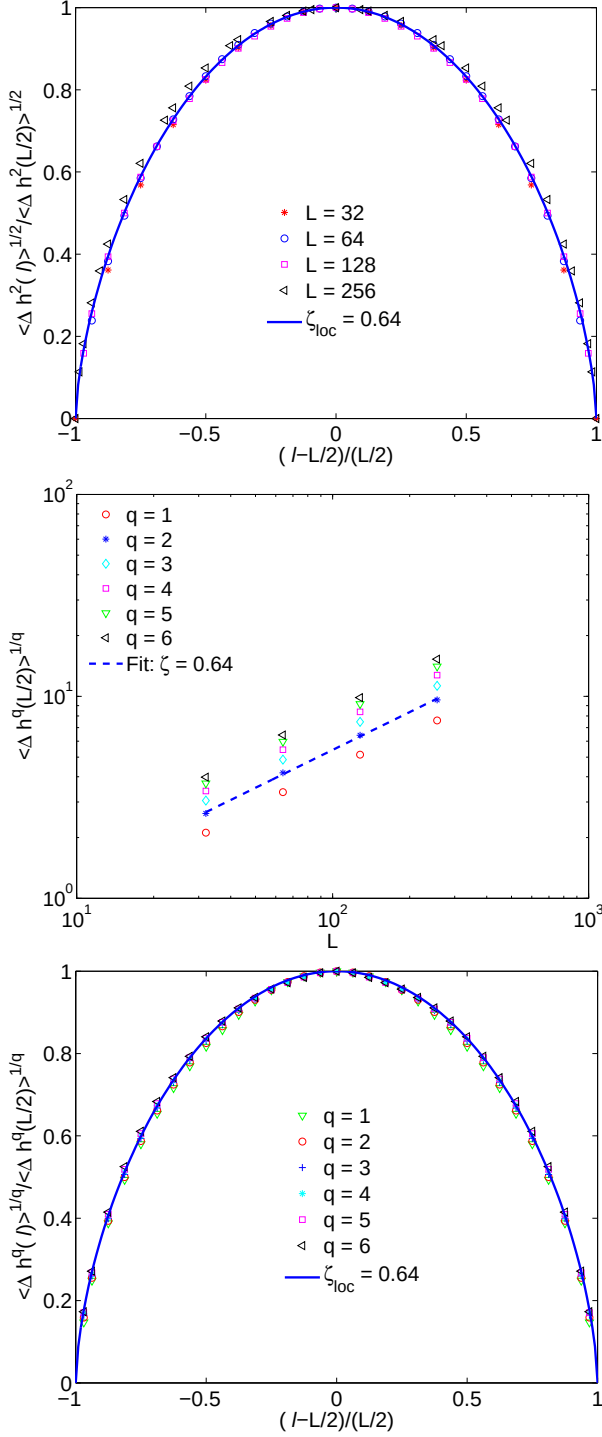


FIG. 4: (Color online) Removing the jumps from the crack profiles eliminates anomalous scaling. Furthermore, multiscaling of crack profiles is also due to the jumps in the crack profiles. (a) Scaling of $\langle \Delta h_P^2(\ell) \rangle^{1/2}$ with window size ℓ shows collapse of data onto Eq. 10 with $\zeta_{loc} = 0.64$. (b) Scaling of $\langle \Delta h_P^2(L/2) \rangle^{1/2}$ with system size L with a scaling exponent of $\zeta = 0.64$. (c) Scaling of $\langle \Delta h_P^q(\ell) \rangle^{1/q}$ with window size ℓ shows that the apparent multiscaling of crack profiles is due to jumps in the profiles.

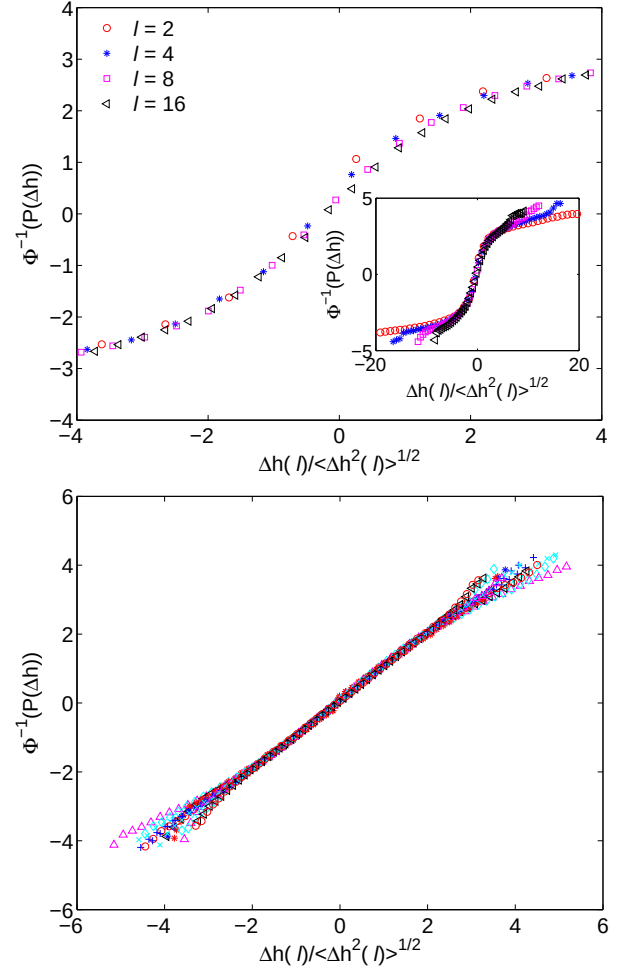


FIG. 5: (Color online) Normal paper plots of cumulative probability distributions $P(\Delta h(\ell))$ of the height differences $\Delta h(\ell) = [h(x + \ell) - h(x)]$ of the crack profile $h(x)$ for various bin sizes ℓ . Φ^{-1} denotes inverse Gaussian. The collapse of the profiles onto a straight line with unit slope would indicate that a Gaussian distribution is adequate to represent $P(\Delta h(\ell))$. (a) $P(\Delta h(\ell))$ distributions for $L = 256$ and $\ell \ll L$. Large deviation from Gaussian profiles is observed for these window sizes. (b) Removing the jumps in the profiles however collapses the $P(\Delta h_P(\ell))$ distributions onto a straight line indicating the adequacy of Gaussian distribution even for small window sizes ℓ . The data is for $L = 128$ with $\ell = (2, 4, 8, 16, 32, 48, 64)$, and $L = 256$ with $\ell = (2, 4, 8, 16, 32, 64, 96, 128)$.

simulations using the beam lattice systems do not exhibit anomalous scaling of roughness in contrast with those obtained using the fuse lattice systems. The local roughness exponent $\zeta_{loc} = 0.65$ obtained using the beam lattice simulations is in good agreement with the earlier results obtained using the central-force spring models ($\zeta_{loc} = 0.65$) [32] and is rather close to that of the fuse models $\zeta_{loc} = 0.72$ [26]. Notice, however, that recently it was shown that for the random fuse model on the square lattice at low disorder the roughness exponent

is larger [34]. This result was attributed to bias due to the lattice topology. In fact, for the triangular lattice this effect is not seen and the roughness exponent is universal [12]. Lattice could also explain the difference between the present result for the beam model ($\zeta_{loc} = 0.65$) and previous disorder dependent results obtained for the square lattice [33].

The agreement in the local roughness exponent between the beam, spring, and possibly fuse models is interesting to note because of these model's dissimilarity in representing deformation of an elastic medium. This seems to imply that the anisotropy in the stress redistribution in tensorial models is irrelevant for the roughness, at least in two dimensions. We even obtain the same local roughness exponent by considering a simplified RBM in which failure events form a connected crack thereby excluding damage nucleation in the bulk. This simplified beam model is similar to the simplified random thresholds fuse model (RFM) considered in the Ref. [18]. In this model, after breaking the weakest beam, successive failure events are only allowed on beams that are connected to the crack. Otherwise, the rules of this simplified model strictly follow those of the usual RBM. Consequently, this model tracks only the connected crack along with its dangling ends in a disordered medium, and hence forms the most simplified model to study the effect of disorder on crack roughness.

As noted in Ref. [18] for the fuse models, this simplified beam model exhibits the same local roughness and power spectra characteristics as that of conventional RBM (see Fig. 6a). This implies that one can expect to obtain same local roughness exponent as long as there exists a fracture process zone around the cracks. Additionally, Fig. 6a indicates the existence of anomalous scaling of roughness as soon as the branching of the cracks is allowed [38]. However, removing the jumps in the crack profiles eliminates this anomalous scaling as can be seen from the collapse of power spectra shown in Fig. 6b. Thus it appears that the anomalous roughness in fracture simulations arises due to crack branching and coalescence of microcracks, which induce jumps in the crack profiles. It should also be noted that anomalous scaling of crack roughness is readily evident in fracture simulations obtained using fuse lattice systems. The reason for this greater propensity to exhibit anomalous scaling in fuse lattice systems appears to be due to scalar nature of fuse systems (anti-planar shear model), which readily allows for crack branching thereby inducing jumps in crack profiles.

Acknowledgment

This research is sponsored by the Mathematical, Information and Computational Sciences Division, Office of Ad-

vanced Scientific Computing Research, U.S. Department of Energy under contract number DE-AC05-00OR22725 with UT-Battelle, LLC. MJA and SZ gratefully thank the financial support of the European Commissions NEST Pathfinder programme TRIGS under contract NEST-

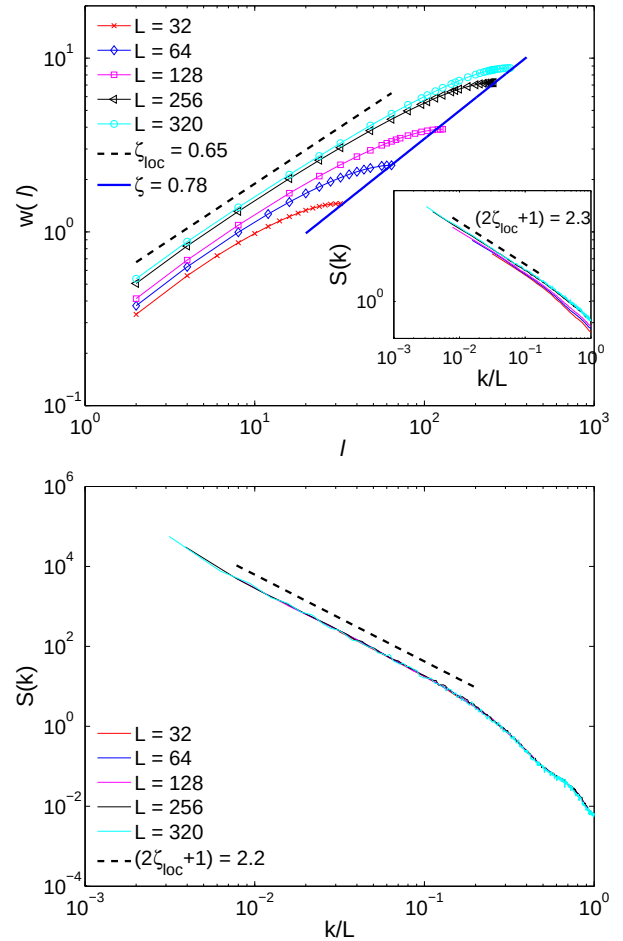


FIG. 6: (Color online) Scaling of crack widths and power spectra for the simplified RBM model. (a) Crack profiles (with jumps) seem to exhibit anomalous roughness scaling. However, the local roughness exponent is same as that noted in conventional RBM. The inset shows the scaling of power spectra, which are parallel to one another but do not collapse onto each other. (b) Collapse of power spectra of crack profiles obtained after removing the jumps in the profiles. Anomalous scaling of roughness in this simplified RBM appears to be due to these jumps in the profiles.

2005-PATH-COM-043386. MJA also acknowledges the financial support from The Center of Excellence program of the Academy of Finland.

[1] H. J. Herrmann and S. Roux (eds.), *Statistical Models for the Fracture of Disordered Media*, (North-Holland, Amsterdam, 1990).

[2] M. J. Alava, P. K. V. V. Nukala, and S. Zapperi, Ad-

- vances in Physics **55**, 349 (2006).
- [3] B. B. Mandelbrot, D. E. Passoja, and A. J. Paullay, Nature (London) **308**, 721 (1984).
 - [4] K.J. Maloy, A. Hansen, E.L. Hinrichsen, and S. Roux, Phys. Rev. Lett. **68**, 213 (1992); E. Bouchaud, G. Lapasset, J. Planés, and S. Navéos, Phys. Rev. B **48**, 2917 (1993).
 - [5] P. Daguer, B. Nghiem, E. Bouchaud, and F. Creuzet, Phys. Rev. Lett. **78**, 1062 (1997).
 - [6] J. Schmittbuhl, S. Roux, and Y. Berthaud, Europhys. Lett. **28**, 585 (1994). J. Schmittbuhl, F. Schmitt, and C. Scholz, J. Geophys. Res. **100**, 5953 (1995).
 - [7] J.J. Mecholsky, D.E. Passoja, and K.S. Feinberg-Ringel, J. Am. Ceram. Soc. **72**, 60 (1989).
 - [8] For a review see E. Bouchaud, J Phys. Condens. Matter **9**, 4319 (1997). E. Bouchaud, Surf. Rev. Lett. **10**, 73 (2003).
 - [9] L. Ponson, D. Bonamy, and E. Bouchaud, Phys. Rev. Lett. **96**, 035506 (2006).
 - [10] D. Bonamy, L. Ponson, S. Prades, E. Bouchaud, and C. Guillot, Phys. Rev. Lett. **97**, 135504 (2006).
 - [11] L. Ponson, D. Bonamy, H. Auradou, G. Mourot, S. Morel, E. Bouchaud, C. Guillot, and J. P. Hulin, Int. J. Fracture **140**, 27 (2006).
 - [12] P. K. V. V. Nukala, S. Zapperi, M. J. Alava, and S. Simunovic, Phys. Rev. E **76**, 056111 (2007).
 - [13] J. M. López, M. A. Rodríguez, and R. Cuerno, Phys. Rev. E **56**, 3993 (1997).
 - [14] J. M. López and J. Schmittbuhl, Phys. Rev. E **57**, 6405 (1998).
 - [15] S. Morel, J. Schmittbuhl, J. M. López, and G. Valentin, Phys. Rev. E **58**, 6999 (1998).
 - [16] S. Zapperi, P. K. V. V. Nukala, and S. Simunovic, Phys. Rev. E **71**, 026106 (2005).
 - [17] P. K. V. V. Nukala, S. Zapperi, and S. Simunovic, Phys. Rev. E **74**, 026105 (2006).
 - [18] M. J. Alava, P. K. V. V. Nukala, and S. Zapperi, J. Stat. Mech.: Theor. Exp. L10002 (2006).
 - [19] J. O. H. Bakke, T. Ramstad, and A. Hansen, Phys. Rev. B **76**, 054110 (2007).
 - [20] S. Santucci, K. J. Maloy, A. Delaplace, J. Mathiesen, A. Hansen, J. O. H. Bakke, J. Schmittbuhl, L. Vanel, and P. Ray, Phys. Rev. E **75**, 016104 (2007).
 - [21] E. Bouchbinder, I. Procaccia, S. Santucci and L. Vanel, Phys. Rev. Lett. **96**, 055509 (2006) E. Bouchbinder, I. Procaccia, and S. Sela, J. Stat. Phys. **125**, 1029 (2006).
 - [22] L. de Arcangelis, S. Redner, and H. J. Herrmann, J. Phys. (Paris) Lett. **46** 585 (1985).
 - [23] A. Hansen, E. L. Hinrichsen, and S. Roux, Phys. Rev. Lett. **66**, 2476 (1991).
 - [24] E. T. Seppälä, V. I. Räsänen, and M. J. Alava Phys. Rev. E **61**, 6312 (2000)
 - [25] J.O.H. Bakke, J. Bjelland, T. Ramstad, T. Strandén, A. Hansen, and J. Schmittbuhl, Phys. Scripta **T106**, 65 (2003).
 - [26] S. Zapperi, P. K. V. V. Nukala, and S. Simunovic, Phys. Rev. E **71**, 026106 (2005).
 - [27] J. Kertész, V. K. Horvath, and F. Weber, Fractals, **1**, 67 (1993).
 - [28] T. Engoy, K. J. Maloy, A. Hansen, and S. Roux, Phys. Rev. Lett. **73**, 834 (1994).
 - [29] L. I. Salminen, M. J. Alava, and K. J. Niskanen, Eur. Phys. J. B **32**, 369 (2003).
 - [30] J. Rosti, L. I. Salminen, E. T. Seppälä, M. J. Alava, and K. J. Niskanen, Eur. Phys. J. B **19**, 259 (2001).
 - [31] I. L. Menezes-Sobrinho, M. S. Couto, and I. R. B. Ribeiro, Phys. Rev. E **71**, 066121 (2005).
 - [32] I. Malakhovskiy, and M. A. J. Michels, Phys. Rev. B **74**, 014206 (2006).
 - [33] B. Skjetne, T. Helle, and A. Hansen, Phys. Rev. Lett. **87**, 125503 (2001).
 - [34] J. O. H. Bakke and A. Hansen, Phys. Rev. Lett. **100** 045501 (2008).
 - [35] J. S. Przemieniecki, Theory of Matrix Structural Analysis, McGraw-Hill Book Company, New York, USA, 1968.
 - [36] P. K. V. V. Nukala, and S. Simunovic, J. Phys. A: Math. Gen. **36**, 11403 (2003).
 - [37] P. K. V. V. Nukala, S. Simunovic, and M. N. Guddati, International Journal for Numerical Methods in Engineering **62**, 1982 (2005).
 - [38] As noted in Ref. [18] for the fuse models, when the branching of the cracks or damage within the fracture process zone is not allowed thereby limiting the crack extension to only the crack tips, a local roughness exponent of 0.5 is obtained and there is no anomalous scaling. As soon as branching is allowed in this simplified RBM model, the value of the roughness exponent increases from $\zeta_{loc} = 0.5$ to $\zeta_{loc} \simeq 0.65$.